



EAST AFRICAN STANDARD

Fishing nets — Determination of breaking force and knot breaking force of netting yarns

EAST AFRICAN COMMUNITY

Foreword

Development of the East African Standards has been necessitated by the need for harmonizing requirements governing quality of products and services in East Africa. It is envisaged that through harmonized standardization, trade barriers which are encountered when goods and services are exchanged within the Community will be removed.

In order to meet the above objectives, the EAC Partner States have enacted an East African Standardization, Quality Assurance, Metrology and Test Act, 2006 (EAC SQMT Act, 2006) to make provisions for ensuring standardization, quality assurance, metrology and testing of products produced or originating in a third country and traded in the Community in order to facilitate industrial development and trade as well as helping to protect the health and safety of society and the environment in the Community.

East African Standards are formulated in accordance with the procedures established by the East African Standards Committee. The East African Standards Committee is established under the provisions of Article 4 of the EAC SQMT Act, 2006. The Committee is composed of representatives of the National Standards Bodies in Partner States, together with the representatives from the private sectors and consumer organizations. Draft East African Standards are circulated to stakeholders through the National Standards Bodies in the Partner States. The comments received are discussed and incorporated before finalization of standards, in accordance with the procedures of the Community.

Article 15(1) of the EAC SQMT Act, 2006 provides that "Within six months of the declaration of an East African Standard, the Partner States shall adopt, without deviation from the approved text of the standard, the East African Standard as a national standard and withdraw any existing national standard with similar scope and purpose".

East African Standards are subject to review, to keep pace with technological advances. Users of the East African Standards are therefore expected to ensure that they always have the latest versions of the standards they are implementing.

© East African Community 2010 — All rights reserved*

East African Community

P O Box 1096

Arusha

Tanzania

Tel: 255 27 2504253/8

Fax: 255-27-2504481/2504255

E-Mail: eac@eachq.org

Web: www.each.int

* © 2010 EAC — All rights of exploitation in any form and by any means reserved worldwide for EAC Partner States' NSBs.

Introduction

In the preparation of this East African Standard, the following sources were consulted extensively:

ISO 1805:2006, *Fishing nets — Determination of breaking force and knot breaking force of netting yarns*

KS 08-1129-2:1992, *Test methods for fishing nets — Part 2: Determination of breaking load of knot and netting yarn*

IS 4303-1:1975, *Code of hygienic conditions for fish industry — Part 1: Pre-processing stage*

IS 4303-2:1975, *Code of hygienic conditions for fish industry — Part 2: Canning stage*

Codex Alimentarius website: http://www.codexalimentarius.net/mrls/pestdes/jsp/pest_q-e.jsp

USDA Foreign Agricultural Service website: <http://www.mrlatabase.com>

USDA Agricultural Marketing Service website: <http://www.ams.usda.gov/AMSV1.0/Standards>

USDA Plant Inspectorate Service website: http://www.aphis.usda.gov/import_export/plants

European Union: http://ec.europa.eu/sanco_pesticides/public

Assistance derived from these sources is hereby acknowledged.

**Fishing nets — Determination of breaking
force and knot breaking force of netting
yarns**

*Filets de pêche — Détermination de la force de rupture et de la force de
rupture au noeud des fils pour filets*



PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

© ISO 2006

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword.....	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions.....	1
4 Principle.....	2
5 Apparatus	2
6 Sampling.....	3
7 Preparation of samples	3
8 Requirements for testing	4
9 Number of tests.....	4
10 Test procedure	4
11 Calculation and expression of results.....	5
12 Test report	6

Draft for comments only - Not to be cited as East African Standard

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 1805 was prepared by the European Committee for Standardization (CEN) Technical Committee CEN/TC 248, *Textiles and textile products*, in collaboration with Technical Committee ISO/TC 38, *Textiles*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This second edition cancels and replaces the first edition (ISO 1805:1973), of which it constitutes a technical revision.

Fishing nets — Determination of breaking force and knot breaking force of netting yarns

1 Scope

This International Standard specifies a method of testing the breaking force and knot breaking force of netting yarns for fishing nets.

Tests may be carried out in both the dry and wet states, but tests in the wet state on the knotted yarn are considered to be particularly appropriate in indicating the behaviour of the yarn in use.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 139, *Textiles — Standard atmospheres for conditioning and testing*

ISO 858, *Fishing nets — Designation of netting yarns in the Tex system*

3 Terms and definitions

For the purposes of this International Standard, the following terms and definitions apply.

3.1

breaking force

force, equal to the maximum force observed during a breaking test

NOTE Distinction is made between

- the dry yarn breaking force,
- the wet yarn breaking force,
- the dry knot breaking force,
- the wet knot breaking force.

3.2

force at rupture

final force at the moment that the specimen or the first component of the specimen breaks at, or after, attainment of the breaking force

NOTE The force at rupture is usually, but not always, identical to the breaking force.

3.3

tenacity

breaking force per unit resultant linear density of the unstrained specimen in the conditioned state

3.4

breaking length

calculated length of a specimen whose conditioned weight exercises a force equal to its breaking force

3.5

time-to-break

time taken to reach the breaking force, measured from the moment of application of the force

NOTE The time-to-break is expressed in seconds.

4 Principle

A length of yarn is extended in the dry or wet state until it reaches the load at rupture. The test is performed using a suitable apparatus that records or indicates the applied force

5 Apparatus

5.1 Tensile testing machine.

5.1.1 Any of the following types may be used:

- a) constant rate of elongation machine;
- b) constant rate of load machine;
- c) constant rate of traverse machine.

Preference should be given to a constant rate of elongation machine.

5.1.2 All tensile testing machines shall include a pair of suitable devices to hold the sample, a means of applying force or elongating the sample at suitable rates, and a force-indicating mechanism which will indicate or continuously record the force applied to the sample.

For determining the breaking force of netting yarns without knots, the samples shall be mounted in special holding devices, for example, of the types shown in Figure 1, to avoid slipping of the samples or breaking due to damage caused by the holding devices.

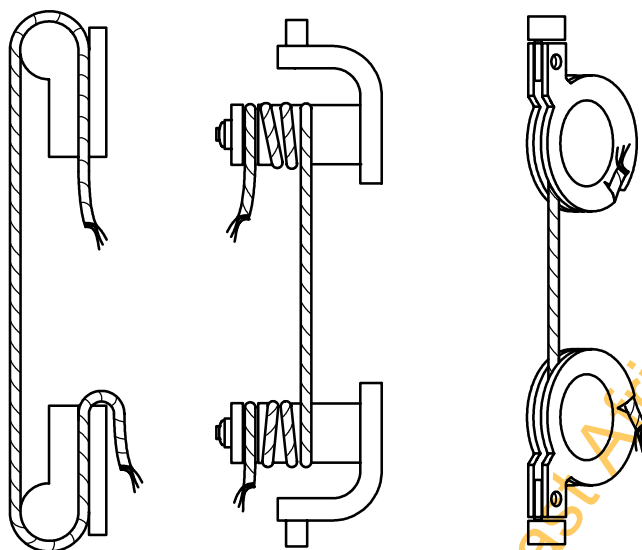


Figure 1 — Holding devices for the testing of netting yarns without knots

5.1.3 The maximum error of the indicated force at any point in the range in which the machine is used shall not exceed $\pm 1\%$. Check the accuracy of the graduated scale of the apparatus dynamically, for example, by means of calibrated springs of appropriate characteristics.

5.1.4 The testing machine shall be capable of testing samples having a nominal gauge length of at least 250 mm.

5.1.5 All testing machines shall include facilities for producing different rates of loading in order to break samples in the specified average time-to-break.

5.2 Equipment for producing and maintaining the standard atmosphere for testing.

See 8.1.

5.3 Equipment in which specimens can be immersed in water preparatory to wet testing.

5.4 Stop-watch or interval timer.

6 Sampling

Sampling shall be carried out in accordance with recognized national standards or in a manner agreed between the parties concerned.

7 Preparation of samples

The samples shall be removed from the package before exposure in the standard atmosphere for testing, or before immersing in water, in such a manner that there is no alteration in the twist.

8 Requirements for testing

8.1 Atmosphere for testing

All samples to be tested in the dry state shall be exposed to the standard atmosphere for testing as described in ISO 139, until they have reached equilibrium. For netting yarns of man-made fibres, a period of 24 h exposure is generally sufficient. Where it is not possible to carry out the tests in the standard atmosphere, the tests shall be carried out immediately after removal of the samples from the standard atmosphere.

8.2 Testing in the wet state

8.2.1 All samples to be tested in the wet state shall be immersed in tap water, without wetting agents, at a temperature of (20 ± 2) °C for a period of not less than 12 h. Surplus water shall be shaken off.

8.2.2 By agreement between the parties, a shorter wetting time with the addition of a wetting agent shall be used. The specimens are immersed for 1 h in solution of wetting agent in water at a temperature of (20 ± 2) °C. A shorter time of immersion is allowed, if it can be shown that the specimen is completely wetted in less than 1 h.

8.3 Distance between the holding devices

The free length of the sample between the holding devices shall be at least 250 mm.

8.4 Time-to-break

The mean duration of the test shall be (20 ± 3) s. It shall be determined by preliminary tests.

Where this time cannot be obtained due to limitations of the apparatus and/or the holding devices, the duration of the test may be (30 ± 3) s or (60 ± 6) s.

This shall be recorded in the test report.

9 Number of tests

At least ten single valid tests on each sample package shall be carried out. If a distinct confidence interval for the mean value is prescribed, as many additional tests shall be carried out as necessary to secure this confidence interval.

10 Test procedure

10.1 General

10.1.1 Check that the distance between the holding devices is at least 250 mm (see 8.3).

10.1.2 Mount the sample in the testing machine so that the axis of the sample is parallel to and coincidental with the direction of the applied force.

10.1.3 Wet samples shall be tested immediately after removal from the water (see 8.2).

10.1.4 Apply the force to reach the prescribed mean time-to-break.

10.1.5 Discard all observations obtained on samples that slip between the holding devices or break due to damage caused by the holding devices. The number of observations discarded as directed above shall be noted.

10.1.6 If any component breaks before the breaking force is reached, this fact shall be recorded in the test report.

10.2 Knotted netting yarns in the dry and wet states

10.2.1 All knots shall be made immediately before testing and gently tightened by hand. Precautions shall be taken to ensure that the twist is not altered.

10.2.2 Samples shall be tested with the weaver's knot. All four ends of the weaver's knot shall be fastened in the holding devices. Each holding device holds the two ends of the same yarn of approximately the same length (see Figure 2).

10.2.3 If a sample does not break at the knot, the test shall be discarded.

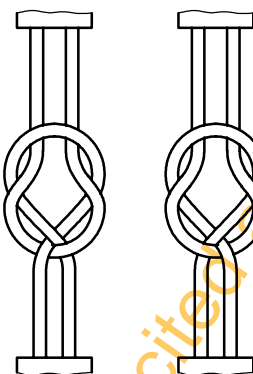


Figure 2 — Weaver's knot

11 Calculation and expression of results

11.1 Average breaking force, in decanewtons (daN), is equal to

$$\frac{\text{sum of observed breaking forces, in decanewtons (daN)}}{\text{number of observations}}$$

Calculate the average breaking force to four significant figures and round it off to three significant figures.

11.2 Average tenacity, in centinewtons per tex, is equal to

$$\frac{\text{average breaking force, in centinewtons (cN)}}{\text{average resultant linear density, in tex, of conditioned sample}}$$

Calculate the average tenacity to four significant figures and round it off to three significant figures.

11.3 Breaking length, in kilometres, is equal to

$$\frac{\text{average breaking force, in decanewtons (daN)}}{\text{average resultant linear density, in kilotex, of conditioned sample}}$$

Calculate the average breaking length to four significant figures and round it off to three significant figures.

11.4 If necessary, the coefficient of variation and the confidence interval shall be calculated by a recognized statistical method.

12 Test report

The test report shall specify the following:

- a) a statement that the tests were performed in accordance with this International Standard;
- b) the date of the test;
- c) the type, linear density, size and direction of final twist of the netting yarn (see ISO 858);
- d) the type and capacity of testing machine used, the type of holding devices employed and the range of indication;
- e) the sampling method employed;
- f) the number of samples tested;
- g) the number of irregular tests;
- h) the kind and time of wetting (with or without wetting agents);
- i) the average breaking force in decanewtons (daN);
- j) any deviation from the specified test procedure.

If it is required, the test report shall also specify:

- k) the coefficient of variation of the breaking force and the confidence interval;
- l) the average tenacity, in centinewtons per tex;
- m) the average breaking length, in kilometres.

Draft for comments only - Not to be cited as East African Standard

Draft for comments only - Not to be cited as East African Standard